



- 1. REFERENCE SPECIFICATION 03700 FOR CONCRETE REBUILD INFORMATION NOT OTHERWISE SHOWN.
- 2. GALVANIC ANODE SIZES AND SHAPES MAY VARY.

	STANDARD DESIGN DETAIL	DRAWING NO. 600 SHEET
HRSD	INSTALLATION OF DISCRETE GALVANIC ANODES	DATE 7/2025

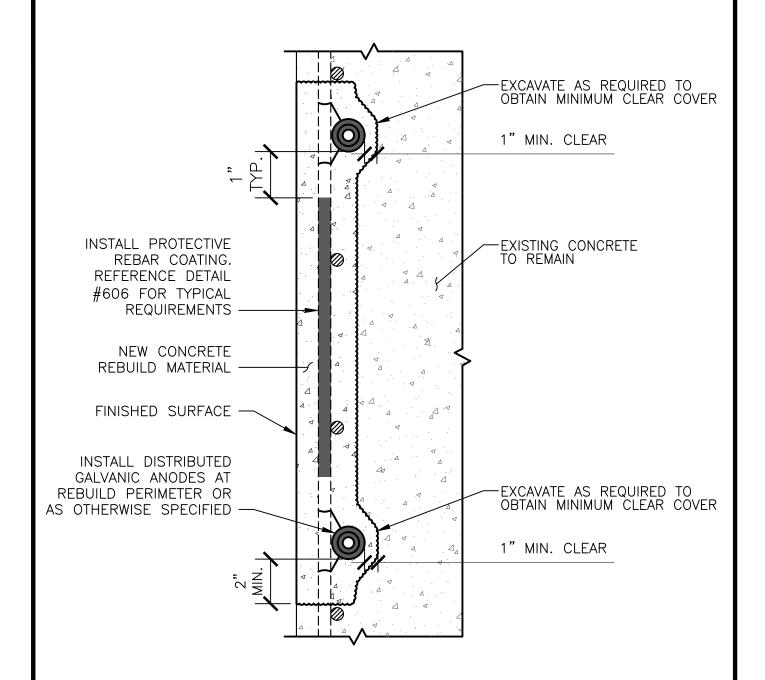



- 1. REFERENCE SPECIFICATION 03700 FOR CONCRETE REBUILD INFORMATION NOT OTHERWISE SHOWN.
- 2. CONDUCTIVE MORTAR NOT SHOWN. ENCAPSULATE ANODES IN CONDUCTIVE MORTAR AS REQUIRED BY MANUFACTURER.
- 3. GALVANIC ANODE SIZES AND SHAPES MAY VARY.


(C) HRSD	STANDARD DESIGN DETAIL	DRAWING NO. 601 SHEET
	INSTALLATION OF DISTRIBUTED GALVANIC ANODES	1 OF 1 DATE 7/2025

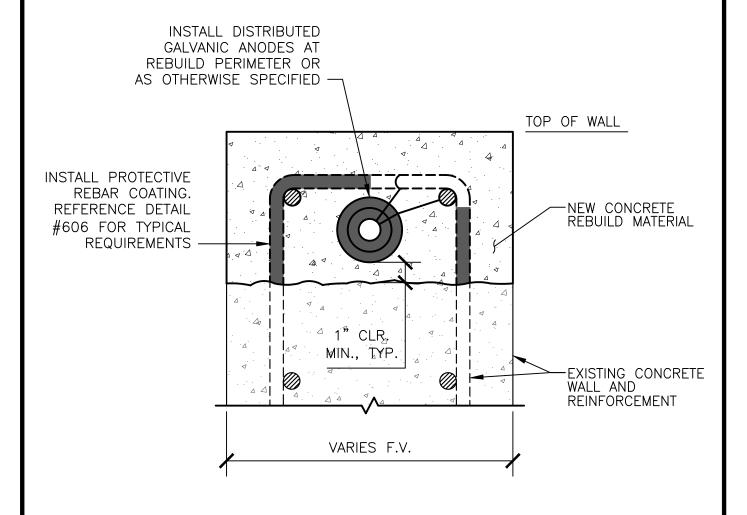

- 1. REFERENCE SPECIFICATION 03700 FOR CONCRETE REBUILD INFORMATION NOT OTHERWISE SHOWN.
- 2. CONDUCTIVE MORTAR NOT SHOWN. ENCAPSULATE ANODES IN CONDUCTIVE MORTAR AS REQUIRED BY MANUFACTURER.
- 3. GALVANIC ANODE SIZES AND SHAPES MAY VARY.




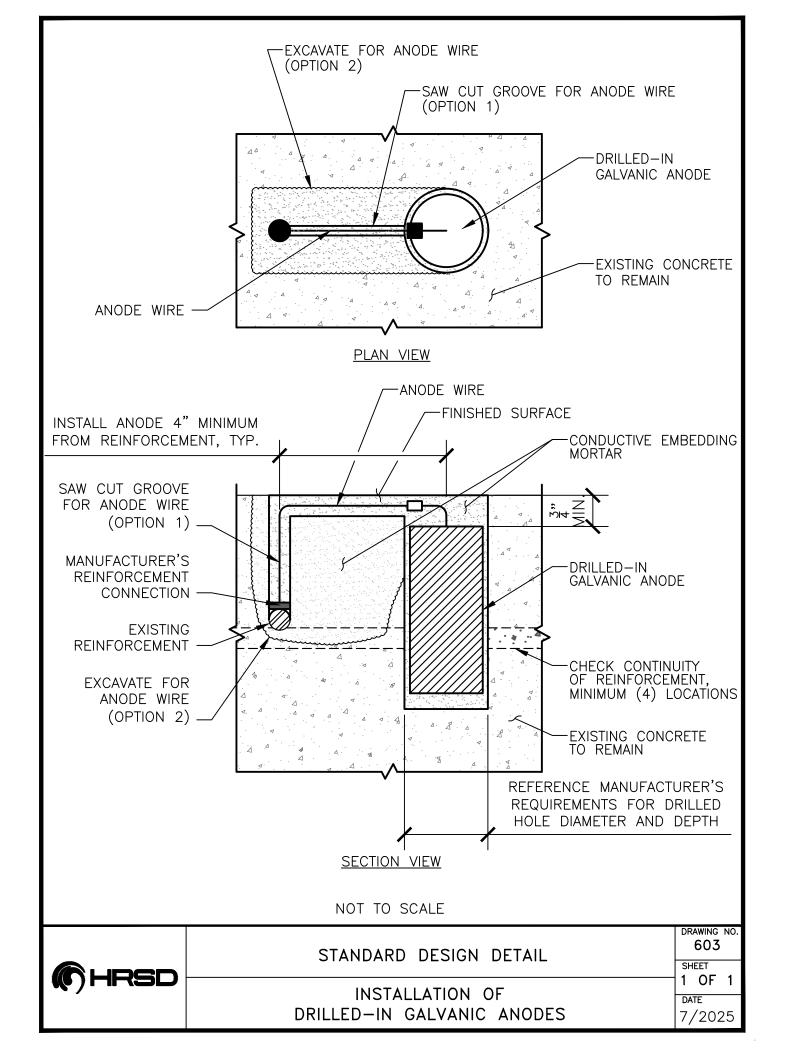

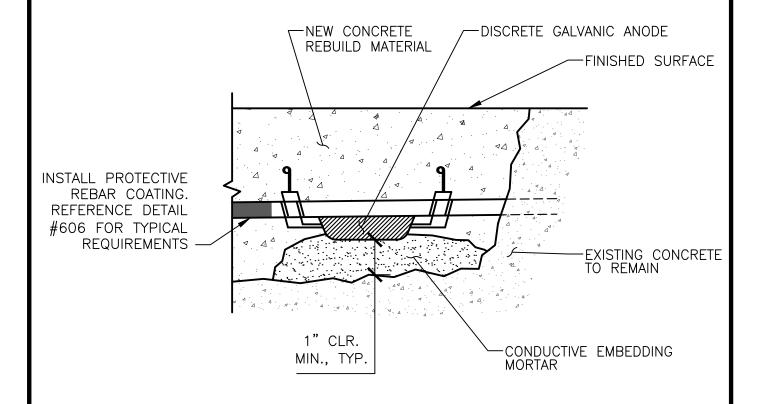


- 1. CONDUCTIVE BEDDED MORTAR SHALL BE INSTALLED FOR ANODES WHEN NEW CONCRETE REBUILD MATERIAL ELECTRICAL RESISTIVITY IS GREATER THAN 15,000 OHM-CM.
- 2. GALVANIC ANODE SIZES AND SHAPES MAY VARY.



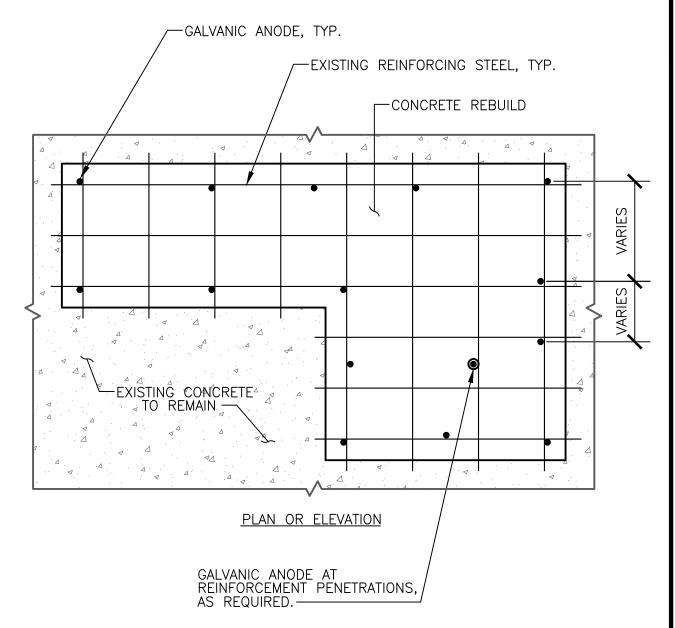


- 1. REFERENCE SPECIFICATION 03700 FOR CONCRETE REBUILD INFORMATION NOT OTHERWISE SHOWN.
- 2. GALVANIC ANODE SPACING SHALL BE IN ACCORDANCE WITH SPECIFICATION REQUIREMENTS.
- 3. SEE DETAIL #606 FOR TYPICAL ANODE CONNECTION DETAILS.




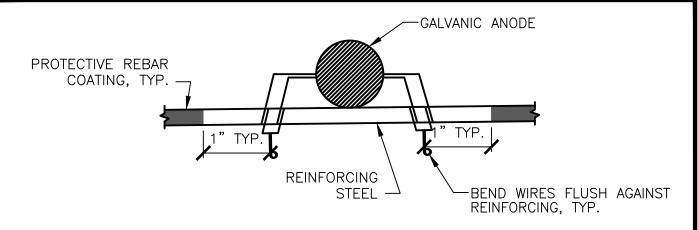

TYPICAL INSTALLATION TO SIDE REBAR

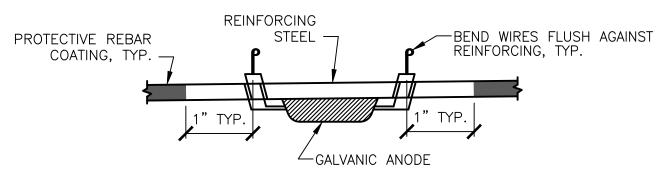


TYPICAL INSTALLATION ABOVE/BELOW REBAR

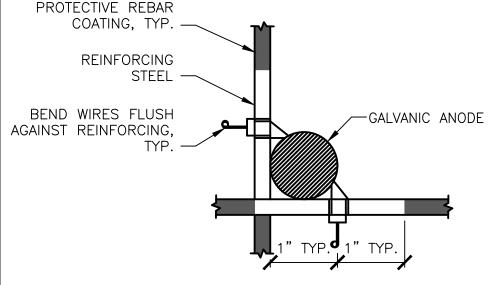



TYPICAL INSTALLATION AT REBAR INTERSECTION


NOTES:

1. GALVANIC ANODE SIZES AND SHAPES MAY VARY.




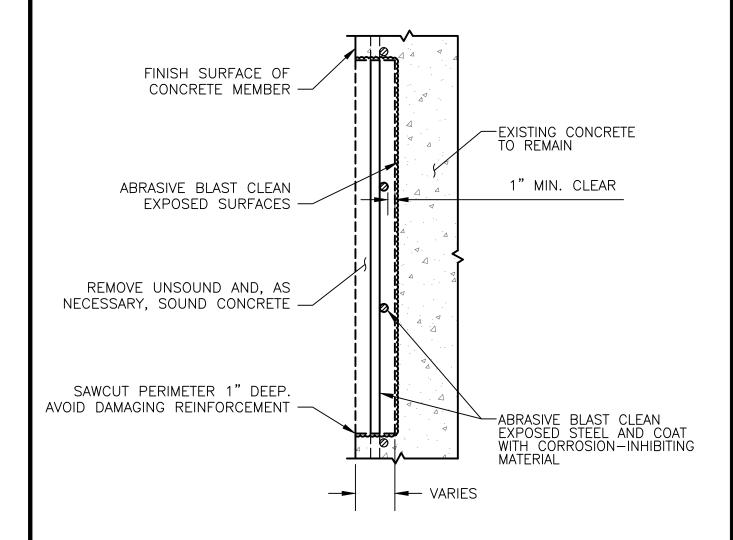




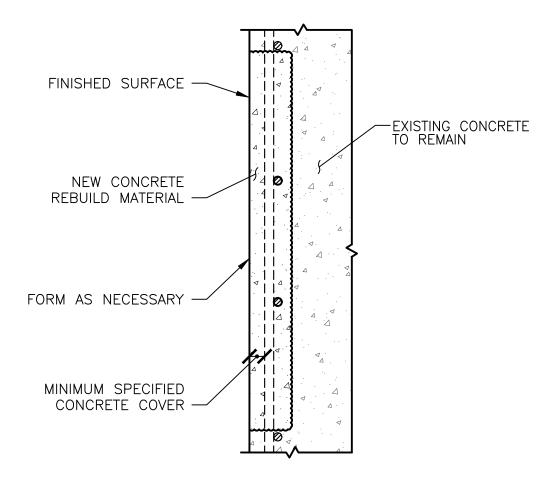


1. GALVANIC ANODES NOT SHOWN FOR CLARITY. REFER TO SPECIFICATION 03800 FOR REQUIREMENTS.



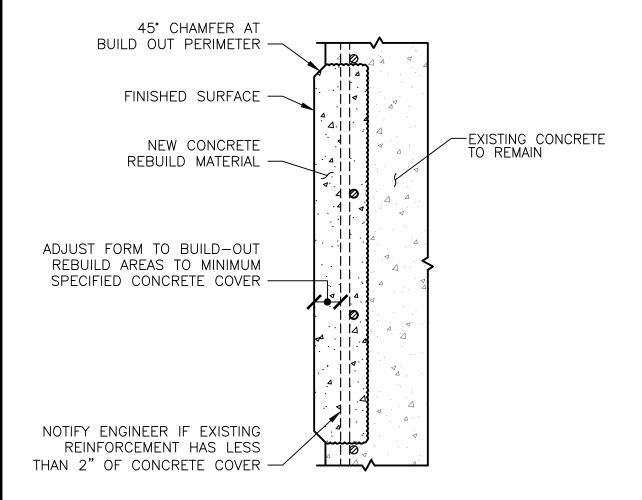


1. GALVANIC ANODES NOT SHOWN FOR CLARITY. REFER TO SPECIFICATION 03800 FOR REQUIREMENTS.



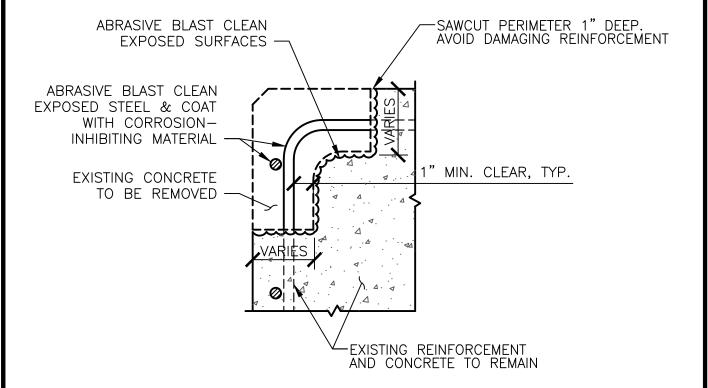


1. GALVANIC ANODES NOT SHOWN FOR CLARITY. REFER TO SPECIFICATION 03800 FOR REQUIREMENTS.



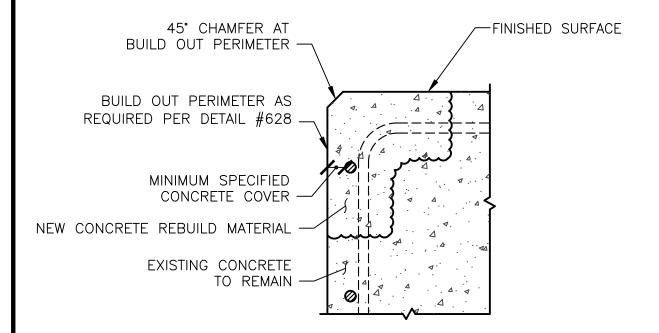

1. GALVANIC ANODES NOT SHOWN FOR CLARITY. REFER TO SPECIFICATION 03800 FOR REQUIREMENTS.



10% SECTION LOSS


BAR	DIAMETER	AREA	BAR DIAMETER WITH 10% SECTION LOSS (IN.)		
NO.	IN.	IN. ²	CIRCUMFERENTIAL LOSS	ONE - SIDED LOSS	
3	0.375	0.110	0.356	0.315	
4	0.500	0.196	0.474	0.420	
5	0.625	0.307	0.593	0.525	
6	0.750	0.442	0.712	0.625	
7	0.875	0.601	0.830	0.735	
8	1.000	0.785	0.949	0.835	
9	1.128	0.999	1.070	0.945	
10	1.270	1.267	1.205	1.060	
11	1.410	1.561	1.338	1.180	




CIRCUMFERENTIAL LOSS ONE - SIDED LOSS



	STANDARD DESIGN DETAIL	SHEET
(C) HRSD	REINFORCING SECTION LOSS TABLE	DATE 7/2025

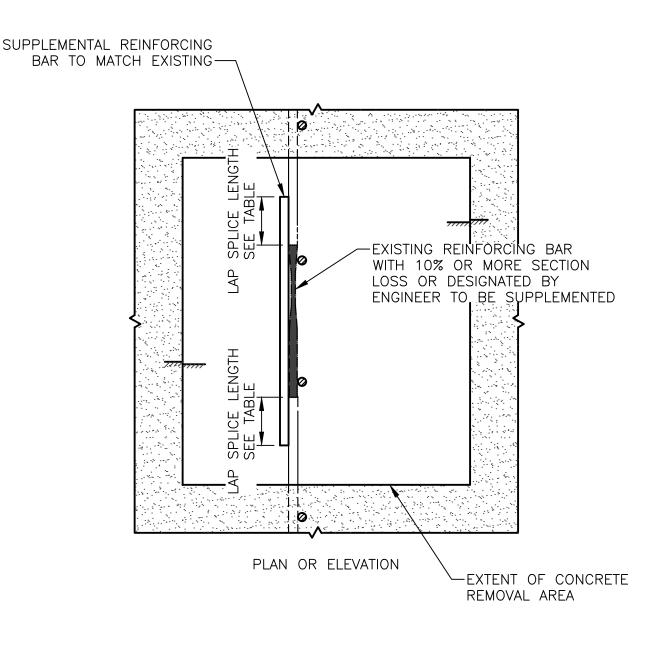




TENSION LAP LENGTH - CLASS B SPLICE - TOP & BOTTOM BARS (GRADE 60 UNCOATED BARS & NORMAL WEIGHT CONCRETE)

BAR NO.	fc=4,000PSI		fc=5,000PSI	
	TOP	вот	TOP	вот
3	15"	12"	13"	12"
4	20"	15"	18"	14"
5	24"	19"	22"	17"
6	29"	22"	26"	20"
7	42"	33"	38"	29"
8	48"	37"	43"	33"
9	60"	46"	54"	41"
10	74"	57"	66"	51"
11	89"	68"	79"	61"

NOTES:

- 1. THIS TABLE IS BASED ON ACI 318-11, EQUATION 12-1 WITH A MINIMUM CLEAR COVER OF 2 INCHES AND MINIMUM CENTER-TO-CENTER BAR SPACING OF 5 INCHES.
- 2. "TOP" BARS ARE HORIZONTAL REINFORCING BARS WITH MORE THAN 12 INCHES OF FRESH CONCRETE CAST BELOW THE BARS AT THE DEVELOPMENT LENGTH. ALL OTHER BARS ARE CONSIDERED "BOT" BARS.
- 3. FOR EPOXY COATED OR ZINC AND EPOXY DUAL COATED BARS, MULTIPLY THE TABLE VALUES BY 1.5 FOR BOTTOM BARS, OR 1.3 FOR TOP BARS. IF THE CONCRETE COVER IS AT LEAST 3X THE BAR DIAMETER AND CLEAR SPACING AT LEAST 6X THE BAR DIAMETER, MULTIPLY VALUES BY 1.2.
- 4. FOR CLASS A SPLICE, DIVIDE VALUES BY 1.3.
- 5. FOR LIGHTWEIGHT CONCRETE, MULTIPLY VALUES BY 1.33.

(C) HRSD	STANDARD DESIGN DETAIL	633 SHEET
(C) HRSD	LAP SPLICE LENGTHS — OPTION 1	DATE 7/2025

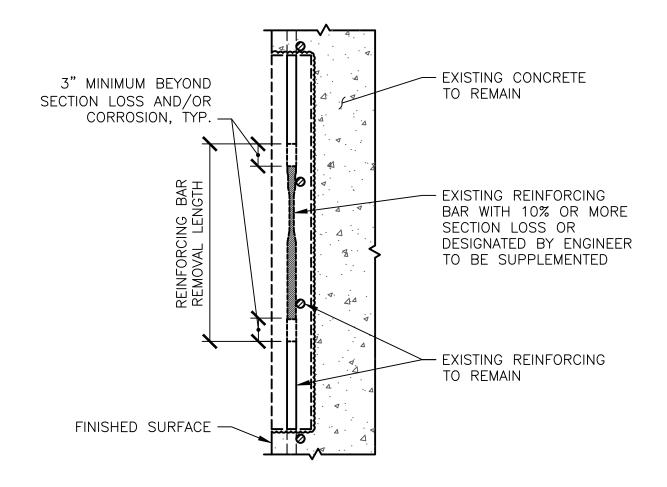

NOT TO SCALE




STANDARD DESIGN DETAIL

DRAWING NO. 634


MECHANICAL SPLICE - OPTION 2 TYPICAL REMOVAL SECTION SHEET
1 OF 1
DATE

7/2025

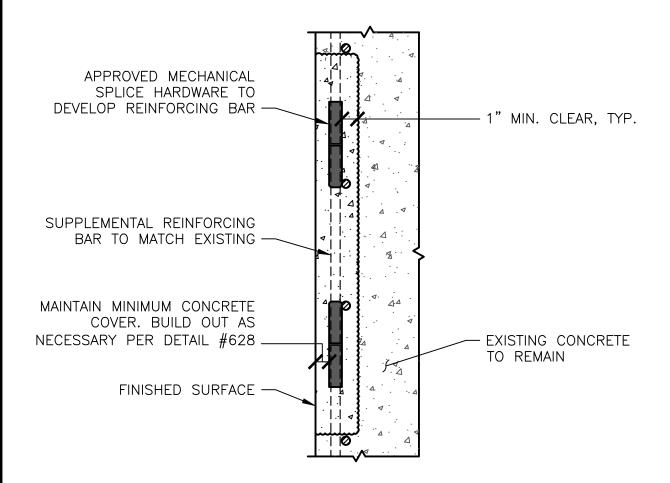

1. GALVANIC ANODES NOT SHOWN FOR CLARITY. REFER TO SPECIFICATION 03800 FOR REQUIREMENTS.



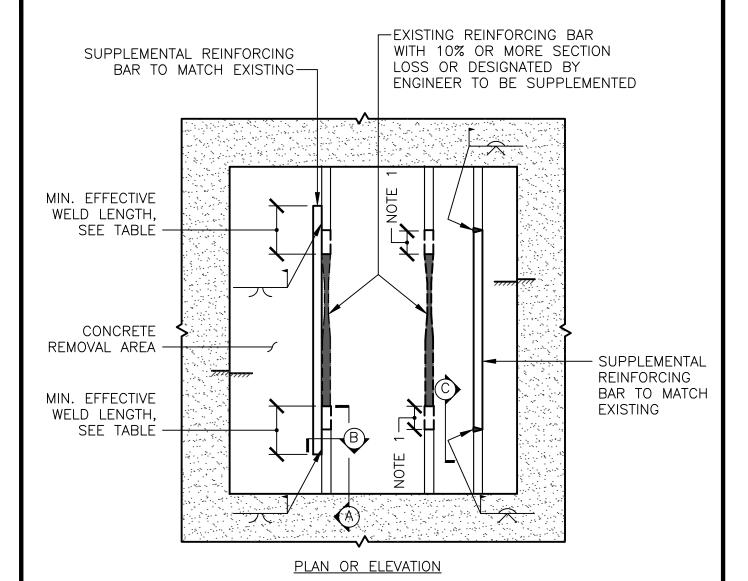


NOTE 1: CUT BAR 3 INCHES MINIMUM BEYOND

SECTION LOSS AND/OR CORROSION AND REMOVE

NOTE 2: SEE DETAILS 637 & 638 FOR SECTIONS

NOTE 3: GALVANIC ANODES NOT SHOWN FOR CLARITY.

REFER TO SPECIFICATION 03800 FOR REQUIREMENTS.




MINIMUM EFFECTIVE LENGTH. SEE TABLE EXISTING BAR

S(E)

SUPPLEMENTAL BAR

GRIND ALL EDGES SMOOTH
AFTER WELDING, TYP

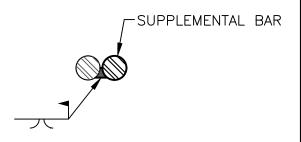

<u>SECTION A - FLARE V - GROOVE WELD SPLICE</u>


SECTION B

WELD SPLICE LENGTHS

BAR NO.	MINIMUM EFFECTIVE WELD LENGTH, in.	BAR RADIUS, S, in.
3	3.5	0.188
4	4.5	0.250
5	5.5	0.313
6	7.0	0.375
7	8.0	0.438
8	9.0	0.500
9	10.0	0.563
10	11.5	0.625
11	12.5	0.688


E-EFFECTIVE THROAT, 0.65 BASED ON E70XX ELECTRODES



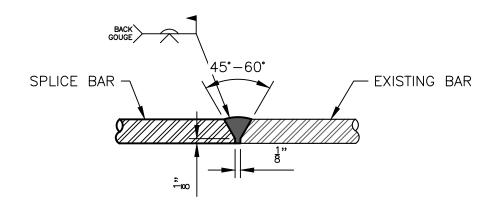


SECTION C - SINGLE V - GROOVE WELD SPLICE




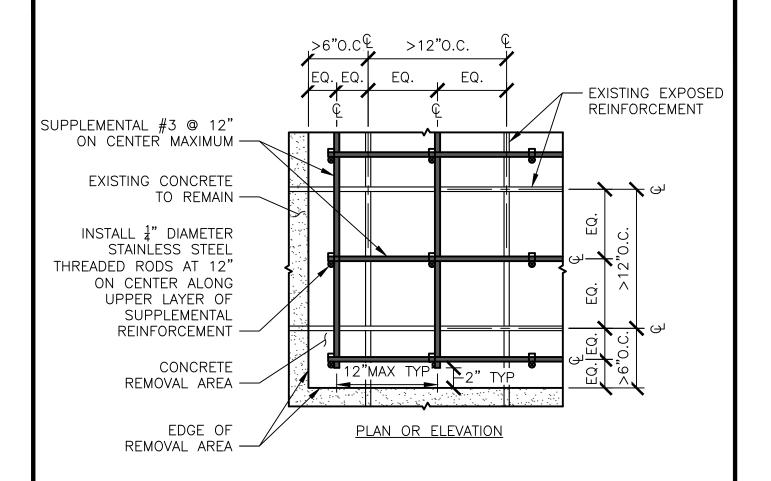


PROVIDE SUPPLEMENTAL REINFORCEMENT FOR EXISTING REINFORCEMENT THAT:

- 1. IS LOCATED 3" OR MORE BELOW NEW CONCRETE SURFACE; OR
- 2. HAS PROVIDED 2" MINIMUM CLEAR COVER, BUT SPACED GREATER THAN 12" O.C.
- 3. IS LOCATED 6" OR MORE FROM EXISTING CONCRETE TO REMAIN.



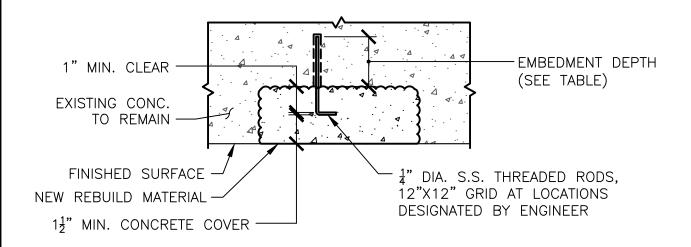

TYPICAL SECTION AT CONC. REMOVAL AREAS - VERTICAL AND OVERHEAD SURFACES

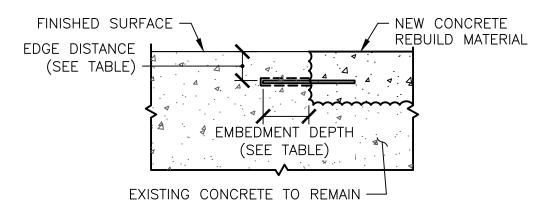


ADHESIVE-GROUTED DOWEL LAYOUT DIMENSIONS


DOWEL SIZE	ALLOWABLE TENSION LOAD PER ANCHOR, Ibs	MINIMUM EMBEDMENT DEPTH, in.	MINIMUM CONCRETE THICKNESS, in.	MINIMUM EDGE DISTANCE, in.	MINIMUM SPACING, in.
¹ ₄ "∅	950	3	6	4.0	8.0
#3	2,100	4	6	6.0	12.0
#4	2,800	4	6	6.0	12.0


NOTES:


- 1. TABLE VALUES FOR SINGLE ANCHORS IN TENSION ONLY; REINFORCING STEEL YIELD STRENGTH OF 60 KSI; THREADED RODS A276, TYPE 316, YIELD STRENGTH OF 30 KSI; HILTI HIT—HY 200 OR HILTI HIT—RE 500 V3 ADHESIVE, 4,000 PSI CONCRETE.
- 2. IF CONDITIONS ARE DIFFERENT THAN THOSE LISTED ABOVE, TABLE VALUES SHALL BE ADJUSTED BY A LICENSED PROFESSIONAL ENGINEER BASED ON ACTUAL DOWEL SYSTEM USED AND REQUIRED DOWEL CAPACITY.

	STANDARD DESIGN DETAIL	DRAWING NO. 640 SHEET
HRSD	ADHESIVE-GROUTED DOWEL LAYOUT	DATE 7/2025

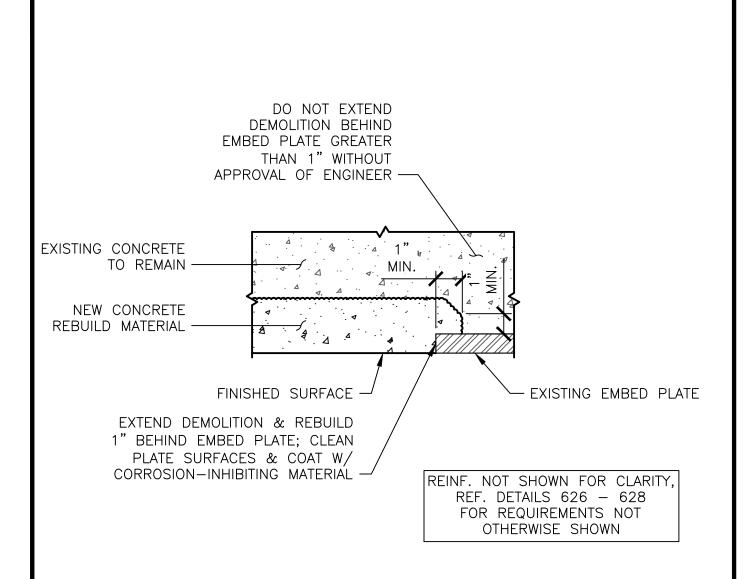



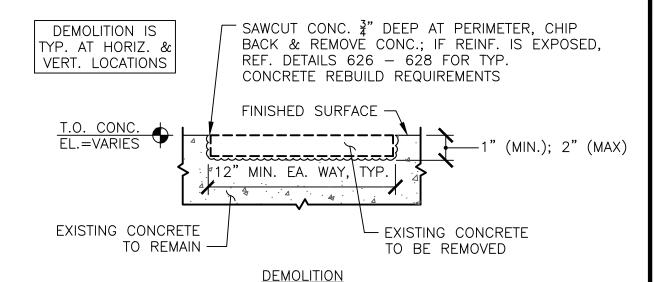


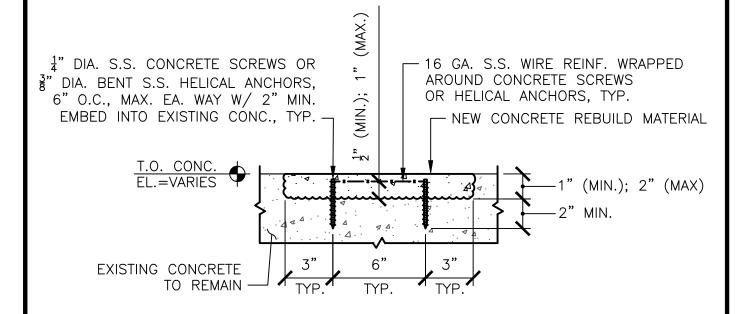


SHALLOW CONCRETE REBUILD - HORIZONTAL




REF. DETAIL #642 FOR TYPICAL DEMOLITION REQUIREMENTS

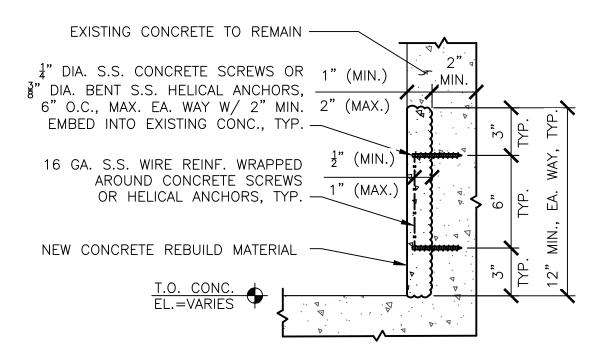

SHALLOW CONCRETE REBUILD - VERTICAL



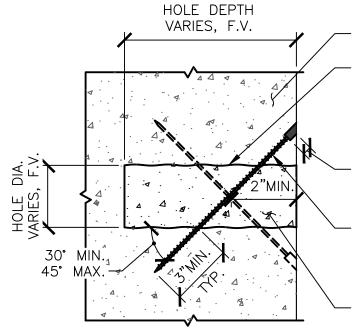

EXISTING CONCRETE

EXISTING PARTIAL—DEPTH CORED HOLE, ROUGHEN & CLEAN INTERIOR SURFACES BY WIRE BRUSHING, THEN FLUSHING W/WATER, TYP.


½" MIN. COUNTERSINK, FILL HOLE W/ SPECIFIED EPOXY REBUILD MATERIAL


(2) ¼"DIA. X 1'-0" LONG S.S. HELICAL ANCHORS AT EA. CORED HOLE LOCATION W/ 3" MIN. EMBEDMENT INTO EXISTING CONCRETE, TYP.


SPECIFIED CONCRETE REBUILD MATERIAL; INSTALL LIFTS PER MANUFACTURER REQUIREMENTS

REBUILD SECTION

INSTALL ANCHORS AROUND PERIMETER OF CORED HOLE PER FIGURE BELOW, TYP.

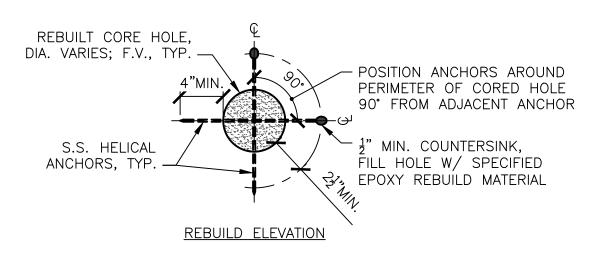



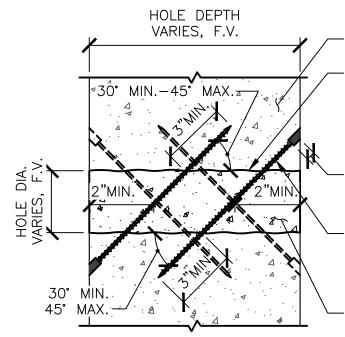

EXISTING CONCRETE

EXISTING FULL—DEPTH CORED HOLE, ROUGHEN & CLEAN INTERIOR SURFACES BY WIRE BRUSHING, THEN FLUSHING W/WATER, TYP.


12" MIN. COUNTERSINK, FILL HOLE W/ SPECIFIED EPOXY REBUILD MATERIAL

(2) ¼"DIA. X 1'-0" LONG S.S. HELICAL ANCHORS AT EA. CORED HOLE LOCATION W/ 3" MIN. EMBEDMENT INTO EXISTING CONCRETE, TYP.


SPECIFIED CONCRETE REBUILD MATERIAL; INSTALL LIFTS PER MANUFACTURER REQUIREMENTS

REBUILD SECTION

INSTALL ANCHORS AROUND PERIMETER OF CORED HOLE PER FIGURE BELOW, TYP.

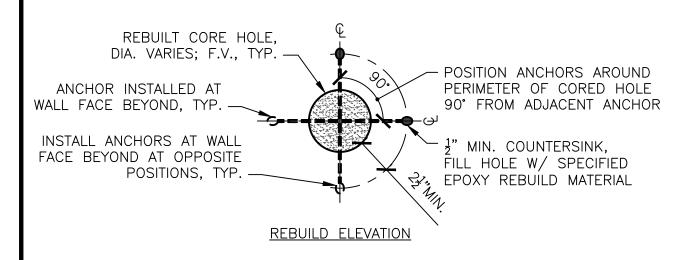




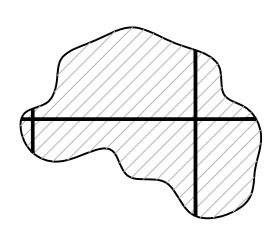

SEE DETAIL 646B FOR SECTION VIEW AND NOTES


(C) HRSD	STANDARD DESIGN DETAIL	DRAWING NO. 646A SHEET
	SPALL REPAIR WITH EXPOSED REINFORCING STEEL	DATE 7/2025

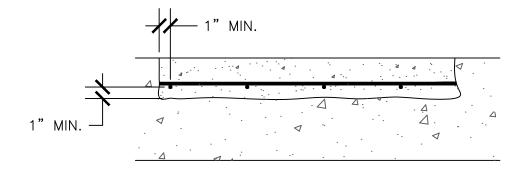


- 1. IF SECTION LOSS OF REBAR IN A MEMBER (SLAB AREA, BEAM OR COLUMN) EXCEEDS 25% THIS REPAIR SHALL BE REVIEWED BY A STRUCTURAL ENGINEER.
- 2. WATER BLAST OR SAND BLAST EXPOSED CONCRETE AND REBAR (SSPC5 WHITE METAL BLAST) IN SPALLED AREA.
- 3. CHIP OUT CONCRETE AROUND EXISTING REBAR TO LEAVE A ONE INCH SPACE (MIN.) BETWEEN REBAR AND CONCRETE. CHIP BACK FURTHER IF NECESSARY TO ACHIEVE SOUND CONCRETE.
- 4. ROUGHEN CONCRETE SURFACE, CLEAN DEBRIS AND DIRT FROM REPAIR AREA, COAT REBAR WITH CORROSION INHIBITOR. WET CONCRETE SURFACE PRIOR TO PLACING NEW CONCRETE.
- 5. CORROSION INHIBITOR SHALL MEET REQUIREMENT OF ASTM C1582.
- 6. CONCRETE SHALL HAVE A MINIMUM COMPRESSIVE STRENGTH OF (f'c) 5000 psi AT AN AGE OF 28 DAYS. MAXIMUM WATER—CEMENT RATIO (W/C) SHALL BE 40% BY WEIGHT. CEMENT SHALL BE ASTM C150 TYPE II WITH A MAXIMUM OF 0.6% ALKALIS BY WEIGHT. CONCRETE SHALL CONTAIN 7% SILICA FUME OR 15% FLYASH AS WEIGHT PERCENT OF CEMENTITIOUS MATERIALS.

(C) HRSD	STANDARD DESIGN DETAIL	646B
	SPALL REPAIR WITH EXPOSED REINFORCING STEEL	DATE 7/2025

DRAWING NO.

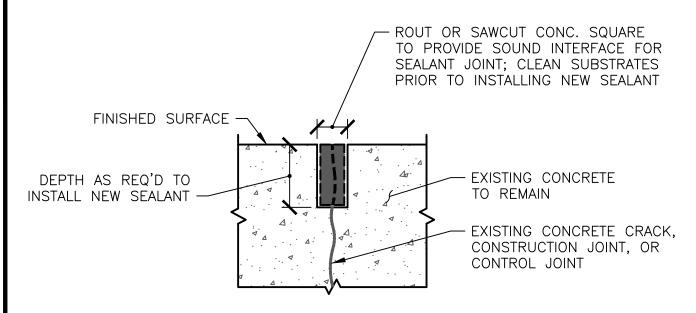

CONCRETE REMOVAL & SURFACE PREPARATION

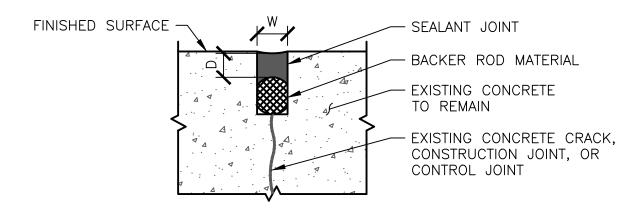

SEALANT JOINT INSTALLATION

HORIZONTAL SEALANT JOINT NOTES

- 1. IF $W < \frac{1}{2}$ "; D = W; $\frac{1}{4}$ " MIN.
- 2. IF $W > \frac{1}{2}$ " TO 1"; $D = (\frac{1}{2})W$
- 3.IF W > 1"; $D = \frac{1}{2}$ "
- 4. ENSURE BACKER ROD DIA. IS $25\%(\pm)$ LARGER THAN WIDTH OF THE JOINT, TYP.

